



BSI Standards Publication

**Polyolefin pipes and fittings — Determination
of carbon black content by calcination
and pyrolysis — Test method**

National foreword

This British Standard is the UK implementation of [ISO 6964:2019](#).

The UK participation in its preparation was entrusted to Technical Committee PRI/88/4, Test Methods - Plastic Piping.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2019
Published by BSI Standards Limited 2019

ISBN 978 0 580 91620 5

ICS 23.040.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2019.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

ISO
6964

Second edition
2019-02-28

**Polyolefin pipes and fittings —
Determination of carbon black
content by calcination and pyrolysis
— Test method**

*Tubes et raccords en polyoléfines — Détermination de la teneur en
noir de carbone par calcination et pyrolyse — Méthode d'essai*



Reference number
ISO 6964:2019(E)



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Principle	1
4 Method A: Electrical tube furnace	2
4.1 Reagents.....	2
4.2 Apparatus.....	2
4.3 Procedure.....	2
4.3.1 Test conditions.....	2
4.3.2 Sampling.....	2
4.3.3 Conditioning.....	2
4.3.4 Silica sample boat preparation for the test.....	2
4.3.5 Test portion.....	3
4.3.6 Determination.....	3
4.4 Calculation and expression of results (Method A).....	3
5 Method B1 or B2: Muffle furnace (conventional B1) or (microwave B2)	4
5.1 Apparatus.....	4
5.2 Procedure.....	4
5.2.1 Test conditions.....	4
5.2.2 Conditioning.....	4
5.2.3 Sampling.....	4
5.2.4 Crucible preparation for the test.....	4
5.2.5 Test portion.....	5
5.2.6 Determination.....	5
5.3 Calculation and expression of results (Method B1 and B2).....	6
6 Method C: Thermogravimetric analyzer (TGA)	6
6.1 Apparatus.....	6
6.2 Procedure.....	6
6.2.1 Conditioning.....	6
6.2.2 Sampling.....	6
6.2.3 Test portion.....	6
6.2.4 Temperature scanning program.....	7
6.2.5 Gas-flow rate.....	7
6.2.6 Determination.....	7
6.3 Calculation and expression of results (Method C).....	7
7 Test report	8

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 5, *General properties of pipes, fittings and valves of plastic materials and their accessories — Test methods and basic specifications*.

This second edition cancels and replaces the first edition (ISO 6964:1986), which has been technically revised. The main changes compared with the last edition are the following:

- Conventional and microwave muffle furnace test methods, and a thermogravimetric analyzer (TGA) test method have been added.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Polyolefin pipes and fittings — Determination of carbon black content by calcination and pyrolysis — Test method

1 Scope

This document specifies test methods for the determination of the carbon black content of polyolefin compositions used in particular for the manufacture of pipes and fittings, and provides a basic specification for polyethylene pipes and fittings.

This document applies equally to the material for manufacture and to any material taken from a pipe or fitting.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

[ISO 11358-1](#), *Plastics — Thermogravimetry (TG) of polymers — Part 1: General principles*

3 Principle

It is possible to determine the carbon black content of polyolefin compositions by one of the following three methods:

- a) Pyrolysis of the sample at (550 ± 50) °C in a stream of nitrogen for 45 min followed by calcination at (900 ± 25) °C, by using an electrical tube furnace (Method A).
- b) Pyrolysis of the sample in a quartz crystal crucible with lid, by using a muffle furnace. According to the type of muffle furnace used there are two different procedures:
 - 1) Conventional muffle furnace (Method B1): pyrolysis from (325 ± 25) °C to (550 ± 25) °C at 15 °C/min and at (550 ± 25) °C for $(10 \pm 0,5)$ min followed by calcination at (900 ± 25) °C.
 - 2) Microwave muffle furnace (Method B2): pyrolysis at (520 ± 25) °C for $(10 \pm 0,5)$ min followed by calcination at (900 ± 25) °C.
- c) Pyrolysis of the sample at a constant rate in a thermogravimetric analyzer (TGA) under inert atmosphere at 800 °C followed by calcination under oxidizing atmosphere at 900 °C (Method C).

NOTE 1 Carbon black is decomposed from 500 °C in air or oxygen. Therefore, the loss observed between 500 °C and 700 °C in air or oxygen corresponds to the overall decomposition of the carbon black.

NOTE 2 If the composition contains, in addition to the carbon black, additives likely to decompose at 900 °C, for example ingredients such as calcium carbonate, the calculation can lead to an over-estimation of the carbon black content. If the ash yield is more than 1 %, further investigation can be required.

Calculate the carbon black content from the difference in mass before and after calcination and pyrolysis.

4 Method A: Electrical tube furnace

4.1 Reagents

4.1.1 Dry nitrogen, having an oxygen content less than 20 ppm, under pressure in a steel cylinder provided with a pressure-reducing valve and flow meter.

NOTE If required, the nitrogen can be purified by bubbling the gas through a pyrogallol solution or by passing it over heated copper tinsel, foil, wire or turnings or by passing it through a gas purifier prior to passing into the furnace.

4.2 Apparatus

4.2.1 Silica combustion sample boat, with a sleeve of 50 mm to 60 mm long.

4.2.2 Electric tube furnace, fitted with a device to allow the sample boat to be inserted and withdrawn. The tube is fitted with nozzles to admit the nitrogen and to evacuate the fumes. A diaphragm closed by means of a glass-wool bung placed behind the entry nozzle ensures that the nitrogen stream is distributed uniformly.

The minimum length of the electric tube furnace should be ≥ 3 times the length of the sample boat, and the minimum length of the quartz tube should be ≥ 7 times the length of the sample boat.

4.2.3 Desiccator, capable of holding the silica sample boat ([4.2.1](#)).

4.2.4 Balance, with an accuracy of $\pm 0,1$ mg.

4.2.5 Timer, with an accuracy of ± 1 s.

4.3 Procedure

4.3.1 Test conditions

Determination of mass shall be carried out in a room at standard temperature (23 ± 2) °C.

4.3.2 Sampling

Test specimen may be in the form of pellet or finished product. In the last case, the specimen shall be reduced to small fragments.

4.3.3 Conditioning

The test sample shall be conditioned for 24 h at (23 ± 2) °C before preparation.

4.3.4 Silica sample boat preparation for the test

Take the silica sample boat which shall be clean and weighed, and proceed as follows:

Place the silica sample boat in the electric tube furnace and adjust the temperature to (900 ± 25) °C. Once this temperature is reached, leave to calcination for approximately 1 h. Then, dry the silica sample boat in the desiccator at room temperature and weigh. Place again the silica sample boat into the desiccator for 30 min and weigh again. This operation shall be repeated until constant mass, i.e. until two consecutive weighing do not differ by more than 0,5 mg. This weighing is recorded as *m*.

4.3.5 Test portion

Three test portions shall be prepared as follows:

Tare the silica sample boat. Weigh, to the nearest 0,1 mg, approximately 1 g of material from the test sample (4.3.2). Record this mass as m_1 .

4.3.6 Determination

The determination on each test sample shall be carried out as described below.

Place the silica sample boat with the test portion (4.3.4) in the inlet of the combustion tube of the electric tube furnace (4.2.2) which has been previously heated to (550 ± 50) °C. Fix the nozzle to the tube inlet and then connect it to the outlet of the nitrogen stream after, if necessary, the nitrogen has passed through the purification system; circulate the nitrogen in the apparatus at a rate of (200 ± 20) cm³/min for approximately 5 min.

Move the combustion tube with the silica sample boat towards the centre of the electric tube furnace, adjust the nitrogen flow rate to (100 ± 10) cm³/min and leave it to pyrolyse for approximately 45 min.

At the end of this period, return the combustion tube with the silica sample boat to the cold section of the electric tube furnace and leave it there for 10 min while maintaining the flow of nitrogen.

Remove the silica sample boat from the combustion tube of the electric tube furnace, allow it to cool in the desiccator (4.2.4) and weigh under the same conditions as prior to the pyrolysis (4.3.3). Record the mass to the nearest 0,1 mg as m_2 .

Place the silica sample boat in the furnace at a temperature of (900 ± 25) °C and calcine until all traces of carbon black have disappeared. Allow it to cool in the desiccator (4.2.4) and weigh under the same conditions as prior to the pyrolysis (4.3.3). Record the mass to the nearest 0,1 mg as m_3 .

4.4 Calculation and expression of results (Method A)

Calculate the carbon black content, expressed as a percentage by mass, from [Formula \(1\)](#).

$$\frac{m_2 - m_3}{m_1} \times 100\% \quad (1)$$

where

m_1 is the mass, in grams, of the test portion;

m_2 is the mass, in grams, of the silica sample boat plus the test portion after pyrolysis at 550 °C;

m_3 is the mass, in grams, of the sample boat plus the test portion after calcination at 900 °C, with ash where appropriate.

Calculate the arithmetic mean of the carbon black content determined on the three test portions and report the result rounded mathematically to two significant figures.

NOTE Where appropriate (see NOTE 2 to [Clause 3](#)), calculate the ash content, expressed as a percentage of the original mass, from [Formula \(2\)](#):

$$\frac{m_3 - m}{m_1} \times 100\% \quad (2)$$

where

m is the mass, in grams, of the silica sample boat;

m_1 is the mass, in grams, of the test portion;

m_3 is the mass, in grams, of the sample boat plus the test portion after calcination at 900 °C, with ash where appropriate.

Calculate the arithmetic mean of the ash content determined on the three test portions and report the result rounded mathematically to two significant figures.

5 Method B1 or B2: Muffle furnace (conventional B1) or (microwave B2)

5.1 Apparatus

5.1.1 Crucible, recipient of quartz crystal with a lid of the same material which closes the recipient just by superposition on the recipient, with approximately 10 ml capacity.

The crucible system generates an inert atmosphere by replacing the air in the crucible due to the gases released by the sample during the pyrolysis. It is important that there is no damage on the crucible edge or on the lid because it would allow air to enter and the consequent burning of the sample.

5.1.2 Desiccator, capable of holding the crucibles ([5.1.1](#)).

5.1.3 Balance, with an accuracy of $\pm 0,1$ mg.

5.1.4 Conventional muffle furnace, for method B1 ([5.2.6.1](#)).

NOTE For a muffle furnace that does not have a programming system, a scan of (15 ± 1) °C/min is equivalent to heating from 300 °C to 500 °C in approximately 15 min and similarly for the cooling scan.

5.1.5 Microwave muffle furnace, for method B2 ([5.2.6.2](#)).

5.1.6 Timer, with an accuracy of (± 1) s.

5.2 Procedure

5.2.1 Test conditions

Determination of mass shall be carried out in a room at standard temperature (23 ± 2) °C.

5.2.2 Conditioning

The test sample shall be conditioned for 24 h at (23 ± 2) °C before preparation.

5.2.3 Sampling

The test specimen may be in the form of a pellet or finished product. In the last case, the specimen shall be reduced to small fragments.

5.2.4 Crucible preparation for the test

Take the crucible which shall be clean and weighed, and proceed as follows:

Place the crucible in the conventional muffle furnace and adjust the temperature to (900 ± 25) °C. Once this temperature is reached, leave to calcinate for approximately 1 h. Then, dry the crucible in the desiccator at room temperature and weigh. Place again the crucible into the desiccator for 30 min and weigh again. This operation shall be repeated until constant mass, i.e. until two consecutive weighing do not differ by more than 0,5 mg. This weighing is recorded as m .

This procedure could be carried out also in a microwave muffle furnace at the same temperature but for 15 min.

5.2.5 Test portion

Three test portions shall be prepared as follows with the mass selected in the range dependent on the equipment used:

Tare the crucible. Weigh, to the nearest 0,1 mg, approximately 1 g to 10 g of the material according to the type of crucible used.

Record this mass as m_1 .

5.2.6 Determination

5.2.6.1 Method B1: Conventional muffle furnace

Place the crucible with lid and with the test portion (5.2.4) in the conventional muffle furnace (5.1.4). The temperature shall be at (325 ± 25) °C. Program the heating scan to $(10 \text{ to } 15 \pm 1)$ °C/min until reaching (550 ± 25) °C. Let it pyrolyze at this temperature for (10 ± 5) minutes. Program cooling scan to (15 ± 1) °C/min until reaching (325 ± 25) °C, initial temperature of the pyrolysis cycle.

Remove the crucible with lid from the muffle furnace and allow it to cool in the desiccator until room temperature is reached. Dry the crucible with lid in the desiccator at room temperature and remove the lid to weigh the crucible. Place the crucible in the desiccator for 30 min and weigh again. This operation shall be repeated until constant mass, i.e. until two consecutive weighing do not differ by more than 0,5 mg. This weighing is recorded as m_2 .

Place the crucible without lid in the muffle furnace and adjust the temperature to (900 ± 25) °C. When this temperature is reached, calcine for (30 ± 5) min.

Turn off the muffle furnace, wait until the temperature has dropped below 500 °C and remove the crucible. Dry the crucible without the lid in the desiccator at room temperature and weigh. Place the crucible in the desiccator for 30 min and weigh again. This operation shall be repeated until constant mass, i.e. until two consecutive weighing do not differ by more than 0,5 mg. This weighing is recorded as m_3 .

5.2.6.2 Method B2: Microwave muffle furnace

Place the crucible with lid and with the test portion (4.2.4) in the microwave muffle furnace (5.1.5), which temperature shall be at (520 ± 25) °C. Leave it to pyrolyse for $(10 \pm 0,5)$ min.

Remove the crucible with lid from the microwave muffle furnace and allow it to cool in the desiccator until room temperature is reached. Dry the crucible with lid in the desiccator at room temperature and weigh the crucible without the lid. Place the crucible in the desiccator for 30 min and weigh again. This operation shall be repeated until constant mass, i.e. until two consecutive weighing don't differ by more than 0,5 mg. This weighing is recorded as m_2 .

Place the crucible without lid in the microwave muffle furnace and adjust the temperature at (900 ± 25) °C. When this temperature is reached, calcine for (10 ± 1) min.

Turn off the microwave muffle furnace, wait until the temperature has dropped below 500 °C and remove the crucible. Cover the crucible with the lid and introduce it in the desiccator at room temperature and weigh the crucible without the lid. Place the crucible in the desiccator for 30 min and weigh again. This operation shall be repeated until constant mass, i.e. until two consecutive weighing do not differ by more than 0,5 mg. This weighing is recorded as m_3 .

5.3 Calculation and expression of results (Method B1 and B2)

Calculate the carbon black content, expressed as a percentage by mass, from [Formula \(3\)](#):

$$\frac{m_2 - m_3}{m_1} \times 100\% \quad (3)$$

where

- m_1 is the mass, in grams, of the original test portion;
- m_2 is the mass, in grams, of the crucible plus the test portion after pyrolysis;
- m_3 is the mass, in grams, of the crucible plus the test portion after calcination, with ash where appropriate.

Calculate the arithmetic mean of the carbon black content determined on the three test portions and report the result rounded mathematically to two significant figures.

NOTE Where appropriate (see NOTE 2, [Clause 3](#)), calculate the ash content, expressed as a percentage of the original mass, from [Formula \(4\)](#):

$$\frac{m_3 - m}{m_1} \times 100\% \quad (4)$$

where m is the mass, in grams, of the crucible.

Calculate the arithmetic mean of the ash content determined on the three test portions and report the result rounded mathematically to two significant figures.

6 Method C: Thermogravimetric analyzer (TGA)

6.1 Apparatus

For the purposes of this document, the instruments suitable for this test method given in [ISO 11358-1](#) shall apply.

6.2 Procedure

6.2.1 Conditioning

The test sample shall be conditioned for 24 h at (23 ± 2) °C before preparation.

6.2.2 Sampling

The test specimen may be in the form of a pellet or finished product. In the last case, the specimen shall be reduced to small fragments.

NOTE This method is suitable for pellet and products containing more than 2 % carbon black.

6.2.3 Test portion

Three test portions shall be prepared from the sample in an appropriate size for the specimen holder. Microtome or razor blades are suitable for this purpose. For each sample portion proceed as follows:

- Cut 15 mg to 40 mg of test sample.
- Tare the sample holder.
- Place the test portion in the sample holder; check whether the mass is between 15 mg and 40 mg.

In case of dispute a sample between 20 mg and 30 mg should be used.

6.2.4 Temperature scanning program

The temperature scan method shall follow the next steps:

- a) Scan at 10 °C/min or at 20 °C/min from 23 °C to 800 °C (under purge of an appropriate inert gas).
- b) Isotherm at 800 °C for 15 min (under purge of an appropriate inert gas).
- c) Without cooling, scan at 10 °C/min or 20 °C/min from 800 °C to 900 °C (under purge of air/oxygen).

6.2.5 Gas-flow rate

Choose the gas-flow rate in accordance with [ISO 11358-1](#) taking into account the equipment used.

6.2.6 Determination

Start the test and determine the percentage of carbon black measuring the mass loss produced from the air or oxygen entering.

In order to determine the percentage of carbon black, the mass loss that the test portion suffers during the heating scan [see [6.2.4 c\)](#)] shall be measured, expressed as a percentage. As the scope of this document only refers to the carbon black content, it is not necessary to obtain all indicated possible data of the curve (see [Figure 1](#)). The values of initial mass at 23 °C (m_i) and after the scan to 900 °C (m_f) the mass loss shall be recorded, as well as the mass of the test portion before the start of the test method (m_s).

6.3 Calculation and expression of results (Method C)

Calculate the carbon black content, expressed as a percentage by mass, from [Formula \(5\)](#):

$$\frac{m_i - m_f}{m_s} \times 100 \% \quad (5)$$

where

- m_s is the mass, in milligrams, of the test portion before the start of the test method;
- m_i is the mass, in milligrams, before mass loss;
- m_f is the mass, in milligrams, after mass loss.

Calculate the arithmetic mean of the carbon black content (in percentage) determined on the three test portions and report the result rounded mathematically to two significant figures.


NOTE 1 Where appropriate (see NOTE 2, [Clause 3](#)), calculate the ash content, expressed as a percentage of the original mass, from [Formula \(6\)](#):

$$\frac{m_f}{m_s} \times 100 \% \quad (6)$$

Calculate the arithmetic mean of the ash content determined on the three test portions and report the result rounded mathematically to two significant figures.

The results obtained from test specimens which have had an anomalous behaviour after the test method, can be rejected.

NOTE 2 Sometimes it is necessary to alternate the calculation of the analysis software with a manual calculation using the software, recording the weight of the test portion in each stage: initially, before the carbon black loss and after carbon black loss.

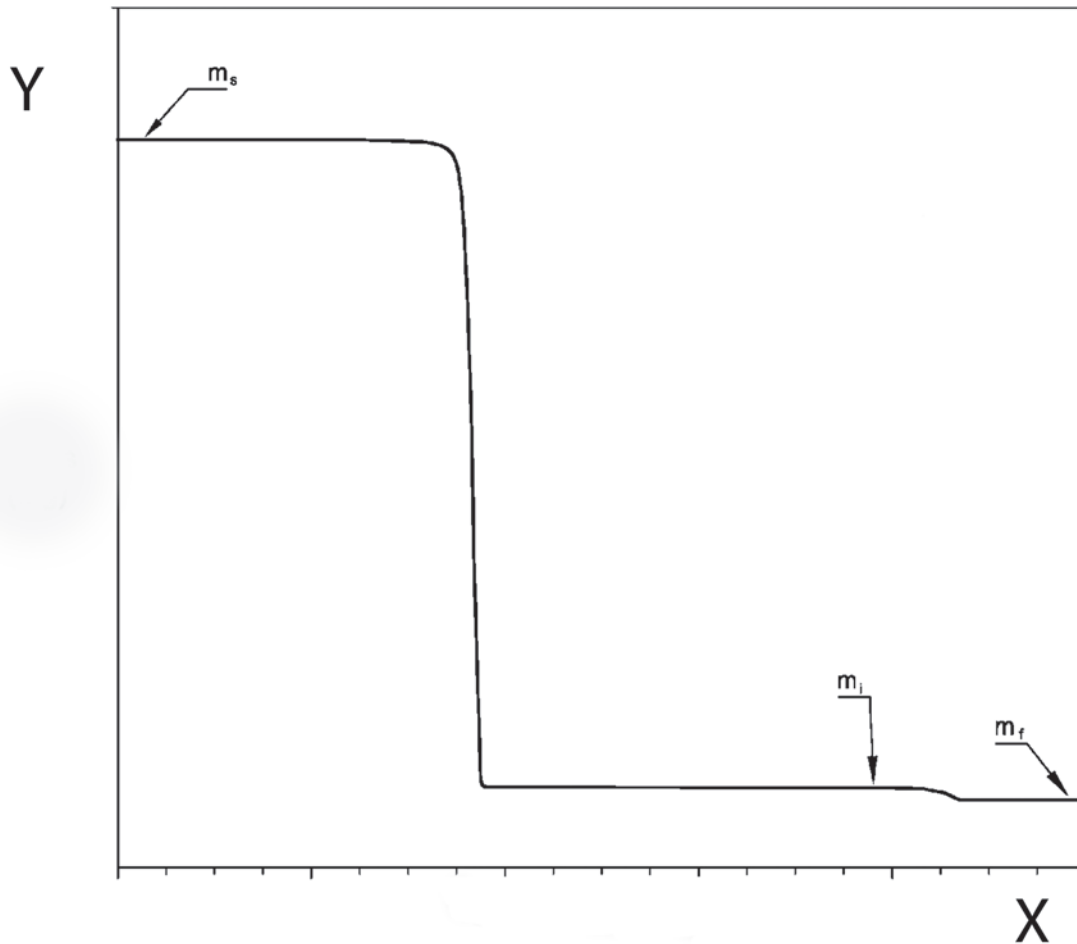

Key

Y mass (mg)

X temperature (°C)/ time (min)

m_s mass, in milligrams, of the test portion before the start of the test method

m_i mass, in milligrams, before mass loss

m_f mass, in milligrams, after mass loss

Figure 1 — Example of a thermogravimetric curve

7 Test report

The test report shall include the following information:

- a) reference to this document, i.e. [ISO 6964:2019](#);
- b) full identification of the sample and the method by which it was taken (from the material delivered, or from the wall of the pipe or from the fitting);
- c) the test method used and number of samples tested;
- d) the carbon black content, expressed as a percentage by mass, calculated as described in each method procedure
 - individual values,
 - mean value,

- e) the presence or absence of ash after calcination; if the value is greater than 1 % of the original mass of the test portion, report the amount and add a note to the report that the carbon black content may be over-estimated;
- f) all operating details not specified in this document, or regarded as optional, as well as any incidents likely to have had an effect on the results;
- g) date of the test.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards -based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.
- Standards purchased in hard copy format:
 - A British Standard purchased in hard copy format is for personal or internal company use only.
 - It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK